

**MECHANICAL, PHYSICAL AND THERMAL
PROPERTIES OF NATURAL FIBRE REINFORCED
EPOXY COMPOSITES**

BY

NURUL SYAZWANI BINTI MOHD HAFIDZ

**A thesis submitted in fulfilment of the requirement for the
degree of Master of Science (Mechanical Engineering)**

**Kulliyyah of Engineering
International Islamic University Malaysia**

OCTOBER 2021

ABSTRACT

There has been expanded effort to offer eco-friendly and biodegradable materials for the next generation of automotive applications due to global environmental concerns and increased awareness of renewable green resources. Currently, polystyrene foam has been used as one of the core insulation material in refrigerated vehicle body which is non-biodegradable and highly polluting resource. There were limited study on utilizing natural fibre in refrigerated vehicle application. Thus, to fill this research gap, current efforts are being made to produce biodegradable and renewable resource composites with the use of palm oil fibre and kenaf fibre in the epoxy resin as a matrix constituent. The objectives of this study were to fabricate palm oil fibre and kenaf fibre reinforced epoxy resin via vacuum infusion techniques based on volume fraction of fibres and alkaline treatment. Then, tensile, water absorption, thermal conductivity and morphologies properties were evaluated and compared with the existing core insulation material (polystyrene foam). As such, the natural fibre composite was fabricated based on two parameters, namely fibre content (20, 30, and 40 vol.%) and 5 w/v% of NaOH solution using vacuum infusion method. The mechanical, physical and thermal properties of fabricated untreated and treated palm oil fibre (UPOF and TPOF) as well as kenaf fibre (UKF and TKF) composites were investigated. From the viewpoint of mechanical performance, 40TPOF showed the highest tensile strength and tensile modulus with the values of 35.89 MPa and 6.39 GPa, respectively. Alkaline treated fibre composite is indeed has increased the values of tensile strength and tensile modulus. It has been proven by the good interfacial adhesion between fibres and matrix detected by SEM morphology. Meanwhile, from the physical perspective, 20TPOF was found to have the lowest water absorption with the values of 1.43%. The use of treated composites increases the number of possible reaction sites on the surface of the fibre and promotes better interfacial bonding within the composite. Fibre adhesion is improved, resulting in dimensionally stable structures. As a result, no voids were observed by using the optical microscope. Besides, the lowest thermal conductivity was 40UPOF with value of 0.079 W/mK. The study of these materials leads to the conclusion that increasing the fibre loading reduces the thermal conductivity of a composite material. The fabrication of the suggested parameters was performed where the obtained values are compared with values of the polystyrene foam. 20TPOF was found to be the most suitable core insulation material with the tensile strength, tensile modulus, water absorption, thermal conductivity values of 25.37 MPa, 3.88 GPa, 1.43% and 0.098 W/mK, respectively. The tensile strength, tensile modulus, and water absorption values have been improved by 97.64%, 99.38%, and 4.67%, respectively compared to the polystyrene foam. Meanwhile, the thermal values obtained for 20TPOF was considered as one of the insulator material. Therefore, this study offers the great potential of the utilization of palm oil fibre and kenaf fibre composites in automotive applications, specifically the core insulation material of refrigerated vehicle body.


ملخص البحث

كان هناك جهد موسع لتقديم مواد صديقة للبيئة وقابلة للتحلل الحيوي للجيل القادم من تطبيقات السيارات بسبب المخاوف البيئية العالمية وزيادة الوعي بالموارد الخضراء المتجددة. حاليًا ، تم استخدام رغوة البوليسترين كواحدة من مواد العزل الأساسية في جسم السيارة المبردة ، وهي مورد غير قابل للتحلل البيولوجي وشديد التلوث. كانت هناك دراسة محدودة حول استخدام الألياف الطبيعية في تطبيقات المركبات المبردة. وبالتالي لسد هذه الفجوة البحثية ، تُبذل الجهود الحالية لإنتاج مركبات الموارد القابلة للتحلل والمتجددة باستخدام ألياف زيت النخيل وألياف التيل في راتنج الإيبوكسي كمكون مصفوفة. هدفت هذه الدراسة إلى تصنيع ألياف زيت النخيل وراتنج الإيبوكسي المعزز بألياف التيل من خلال تقنيات التسريب بالتفريغ بناءً على الجزء الحجمي للألياف والمعالجة القلوية. بعد ذلك ، تم تقييم خصائص الشد وامتصاص الماء والتوصيل الحراري والتشكيلات ومقارنتها مع مادة العزل الأساسية الموجودة (رغوة البوليسترين). تم تصنيع مركب الألياف الطبيعية بناءً على معاملين ، وهما محتوى الألياف (20 ، 30 ، و 40 حجمًا٪) و 5 وزن / حجم٪ من محلول هيدروكسيد الصوديوم باستخدام طريقة التسريب بالتفريغ. تم فحص الخواص الميكانيكية والفيزيائية والحرارية لألياف زيت النخيل المصنعة غير المعالجة والمعالجة (UPOF و TPOF) ، وكذلك مركبات ألياف التيل (UKF و TKF). من وجهة نظر الأداء الميكانيكي ، أظهر 40TPOF أعلى قوة شد ومعامل شد بقيمتين 35.89 ميغا باسكال و 6.39 جيغا باسكال على التوالي. مركب الألياف القلوية المعالج بالفعل قد زاد من قيم قوة الشد ومعامل الشد. لقد تم إثبات ذلك من خلال الالتصاق البيئي الجيد بين الألياف والمصفوفة التي تم الكشف عنها بواسطة مورفولوجيا SEM. وفي الوقت نفسه ، من الناحية الفيزيائية ، وجد أن 20TPOF لديها أقل امتصاص للماء بقيمة 1.43٪. يزيد استخدام المركبات المعالجة من عدد مواقع التفاعل المحتملة على سطح الألياف ويعزز الترابط البيئي داخل المركب. نتيجة لذلك ، تم تحسين الالتصاق بالألياف ، مما ينتج عنه هياكل ثابتة الأبعاد. نتيجة لذلك ، لم يتم ملاحظة أي فراغات باستخدام المجهر

الضوئي. إلى جانب ذلك ، كان 40UPOF أقل موصلية حرارية بقيمة 0.079 واط / مللي كلفن. خلصت دراسة هذه المواد إلى أن زيادة تحميل الألياف يقلل من التوصيل الحراري للمادة المركبة. تم إجراء تصنيع المعلمات المقترحة حيث تمت مقارنة القيم التي تم الحصول عليها مع قيم رغوة البوليسترين. 20TPOF كانت أنسب مادة عازلة أساسية مع قوة الشد ، معامل الشد ، امتصاص الماء ، و قيم التوصيل الحراري 25.37 ميغا باسكال ، 3.88 جيجا باسكال ، 1.43% و 0.098 واط / مللي كلفن على التوالي. بالمقارنة مع رغوة البوليسترين ، تم تحسين قيم مقاومة الشد ومعامل الشد وامتصاص الماء بنسبة 97.64% و 99.38% و 4.67% على التوالي. وفي الوقت نفسه ، تم اعتبار القيم الحرارية التي تم الحصول عليها ل 20TPOF كواحدة من مواد العازل. لذلك ، توفر هذه الدراسة إمكانات كبيرة لاستخدام ألياف زيت النخيل ومركبات ألياف التيلف في تطبيقات السيارات ، وتحديدًا مادة العزل الأساسية لهيكل المركبات المبردة.

APPROVAL PAGE

I certify that I have supervised and read this study and that in my opinion, it conforms to acceptable standards of scholarly presentation and is fully adequate, in scope and quality, as a thesis for the degree of Master of Science (Mechanical Engineering)

.....

Muhammad Saifuddin bin
Mohamed Rehan
Supervisor

.....
Hanan binti Mokhtar
Co-Supervisor

I certify that I have read this study and that in my opinion it conforms to acceptable standards of scholarly presentation and is fully adequate, in scope and quality, as a thesis for the degree of Master of Science (Mechanical Engineering)

.....
Hazleen Anuar
Internal Examiner

.....
Siti Norasmah Surip
External Examiner

This thesis was submitted to the Department of Mechanical Engineering and is accepted as a fulfilment of the requirement for the degree of Master of Science (Mechanical Engineering).

.....
Fadly Jashi Darsivan
Head, Department of Mechanical
Engineering

This thesis was submitted to the Kulliyah of Engineering and is accepted as a fulfilment of the requirement for the degree of Master of Science (Mechanical Engineering).

.....
Sany Izan Ihsan
Dean, Kulliyah of Engineering


DECLARATION

I hereby declare that this thesis is the result of my own investigations, except where otherwise stated. I also declare that it has not been previously or concurrently submitted as a whole for any other degrees at IIUM or other institutions.

Nurul Syazwani Binti Mohd Hafidz

Signature.....

Date.....

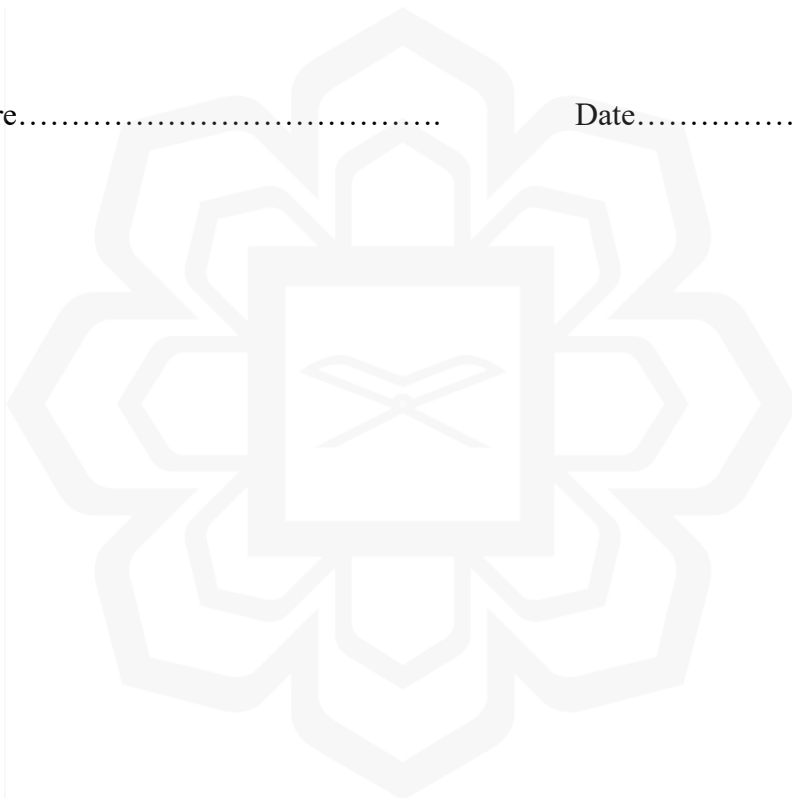

INTERNATIONAL ISLAMIC UNIVERSITY MALAYSIA

**DECLARATION OF COPYRIGHT AND AFFIRMATION OF
FAIR USE OF UNPUBLISHED RESEARCH**

**MECHANICAL, PHYSICAL AND THERMAL PROPERTIES OF
NATURAL FIBRE REINFORCED EPOXY COMPOSITES**

I declare that the copyright holder of this thesis is jointly owned by the student and IIUM.

Copyright © 2021 Nurul Syazwani binti Mohd Hafidz and International Islamic University Malaysia. All rights reserved.

No part of this unpolished research may be reproduced. Stored in a retrieval system, or transmitted, in any form or by any means, electronic, mechanical, photocopying, recording or otherwise without prior written permission of the copyright holder expect as provided below

1. Any material contained in or derived from this research may be used by others in the writing with due acknowledgement.
2. IIUM or its library will have the right to make and transmit copies (print or electronic) for institution and academic purposes.
3. The IIUM library will have the right to make, store in a retrieved system and supply copies of this unpublished research if requested by other universities and research libraries.

By signing this form, I acknowledged that I have read and understand the IIUM Intellectual Property Right and Commercialization policy.

Affirmed by Nurul Syazwani binti Mohd Hafidz

.....
Signature

.....
Date

ACKNOWLEDGEMENTS

In the name of Allah, the Most Gracious and the Most Merciful.

First of all, all praise to the Almighty One, Allah for giving the opportunity to live in this world and giving a good health that I, capable of to do my daily task peacefully, and able to fulfil my responsibilities as a servant of God. Alhamdulillah.

Special thanks go to:

My parents, Mr. Mohd Hafidz bin Ibrahim and Mrs. Rozita binti Ibrahim for supporting and encouraging me to continue this research until it is done. They never failed to give me support whenever I had some problems in doing my research and they are always being there for me. Thank you so much for the love and endless support throughout my master's journey.

Besides my parents, I would like to express my deepest gratitude and appreciation to my supervisor, Dr. Muhammad Saifuddin Mohamed Rehan and my co-supervisor, Dr. Hanan Mokhtar, who helped me and giving guidance in completing the study. They gave opinions on how to conduct the study and explained about how to do this research so that I could understand better about the study. Their guidance helped me in all the time of research and writing of this thesis. I could not have imagined having a better advisor and mentor for my master's study.

My special thanks also go to Mr. Fuat from Malaysian Palm Oil Board (MPOB). He was one of the persons in charge who was sincerely helping me by providing the raw materials of palm oil fibre without any charges. I would never forget by his kindness to help me in completing my research.

Last but not least, to those who have contributed directly and indirectly, thank you very much. Without the continuous help, I would not be able to reach this far.

TABLE OF CONTENTS

Abstract	ii
Abstract in Arabic	iii
Approval Page.....	v
Declaration	vi
Copyright Page.....	vii
Acknowledgements	viii
List of Tables	xii
List of Figures	xiii
List of Abbreviations	xvii
List of Symbols	xix
CHAPTER ONE: INTRODUCTION	1
1.1 Background	1
1.2 Problem Statement	3
1.3 Objectives of Study	5
1.4 Scope of Study	5
CHAPTER TWO: LITERATURE REVIEW	7
2.1 Introduction	7
2.2 Polymer Composites in Automotive Applications.....	8
2.2.1 Refrigerated Vehicles	9
2.2.2 Polyurethane	11
2.2.3 Polystyrene	13
2.3 Introduction to Natural Fibres	15
2.3.1 Type of Fibres.....	15
2.4 Classification of Natural Fibres	18
2.4.1 Classification of Plant Fibres.....	18
2.4.2 Palm Oil Fibre Overview.....	19
2.4.3 Palm Oil Fibre	20
2.4.4 Palm Oil Fibre and Its Composites.....	21
2.4.5 Kenaf Overview.....	25
2.4.6 Kenaf Fibre	26
2.4.7 Kenaf Fibre and Its Composites	27
2.5 Barrier in Developing Natural Fibre Composites	30
2.6 Epoxy Resin	32
2.7 Fabrication Method	34
2.7.1 Vacuum Infusion Method.....	37
2.8 Factors Affecting Performances of Composites	40
2.8.1 Effect of Fibre Contents Towards Performances of Composites	40
2.8.2 Effect of Alkaline Treatment of Fibres Towards Performances of Composites	44
2.9 Summary	50
CHAPTER THREE: RESEARCH METHODOLOGY	51
3.1 Introduction	51

3.2	Raw Materials	51
3.2.1	Palm Oil Fibre and Kenaf Fibre	51
3.2.2	Epoxy	53
3.3	Experimental Procedures	53
3.4	Fabrication of Palm Oil Fiber Composites and Kenaf Fiber Composites Using Vacuum Infusion Method	57
3.4.1	Rule of Mixtures of Fibre Composites	57
3.4.2	Alkaline Treatment of Fibres.....	58
3.4.3	Fabrication of Natural Fibre Composites Via Vacuum Infusion.....	60
3.5	Testing of Raw Materials and Natural Fibre Composites.....	62
3.5.1	Fourier Transform Infra-Red (FTIR) Analysis.....	62
3.5.2	Differential Scanning Calorimetry (DSC).....	62
3.5.3	Scanning Electron Microscope (SEM)	62
3.5.4	Optical Microscope.....	63
3.5.5	Tensile Properties	63
3.5.6	Water Absorption	64
3.5.7	Thermal Conductivity.....	65
3.6	Summary	66
CHAPTER FOUR: RESULTS AND DISCUSSION.....		67
4.1	Introduction	67
4.2	Characterization of Raw Materials.....	68
4.2.1	Morphological Properties	68
4.2.2	Fourier Transform Infra-Red (FTIR) Analysis.....	71
4.3	Effects of Fibre Loadings and Alkaline Treatment of Fibres on The Mechanical Properties of Palm Oil Fibre Composites and Kenaf Fibre Composites.....	79
4.3.1	Tensile Properties of Palm Oil Fibre Composites	79
4.3.2	Tensile Properties of Kenaf Fibre Composites.....	86
4.3.3	Morphological Properties	92
4.3.3.1	Tensile Fractured of Palm Oil Fibre Composites	92
4.3.3.2	Tensile Fractured of Kenaf Fibre Composites.....	96
4.4	Effects of Fibre Loadings and Alkaline Treatment of Fibres on The Physical Properties of Palm Oil Fibre Composites and Kenaf Fibre Composites.....	100
4.4.1	Water Absorption	100
4.5	Effects of Fibre Loadings and Alkaline Treatment of Fibres on The Thermal Properties of Palm Oil Fibre Composites and Kenaf Fibre Composites.....	112
4.5.1	Differential Scanning Calorimetry (DSC).....	112
4.5.2	Thermal Conductivities of Palm Oil Fibre Composites	117
4.5.3	Thermal Conductivities of Kenaf Fibre Composites.....	119
4.6	Comparing The Palm Oil Fibre and Kenaf Fibre Reinforced Epoxy Composites With The Existing Core Material Insulation (Polystyrene Foam)	121
4.6.1	Tensile Properties	121
4.6.2	Water Absorption Behaviour.....	123
4.6.3	Thermal Conductivity Properties.....	125

4.7 Comparing The 20TPOF Composite With The Existing Core Material Insulation (Polystyrene Foam)	127
4.8 Summary	129
CHAPTER FIVE: CONCLUSION AND RECOMMENDATIONS	130
5.1 Conclusion	130
5.2 Recommendation For Future Works	132
REFERENCES.....	133
LIST OF PUBLICATIONS	151



LIST OF TABLES

Table 2.1	The development of palm oil fibre composites by varying the usage of polymers	24
Table 2.2	Tensile strength of natural fibre with different of polymers from previous studies	29
Table 2.3	Tensile modulus of natural fibre with different of polymers from previous studies	29
Table 2.4	Various fabrication methods of fibre reinforced composites	35
Table 2.5	Developments of composite materials from various fabrication methods	36
Table 3.1	Details of experiment by stages	56
Table 3.2	Specimen parameters of palm oil fibre composites	60
Table 3.3	Specimen parameters of kenaf fibre composites	60
Table 4.1	Optical microscope image of palm oil fibre composites at 5x magnification with different fibre loadings	104
Table 4.2	Optical microscope image of kenaf fibre composites at 5x magnification with different fibre loadings	110
Table 4.3	Tensile strength and tensile modulus values	123
Table 4.4	Water absorption values	125
Table 4.5	Thermal conductivity values	127
Table 4.6	Tensile, water absorption and thermal values of 20TPOF and polystyrene foam	129

LIST OF FIGURES

Figure 2.1	Refrigerated vehicle (Uwa et al., 2019)	10
Figure 2.2	Polyurethane foam board (Ravago, 2014)	11
Figure 2.3	Polystyrene foam board (Ravago, 2020)	11
Figure 2.4	Polyurethane synthesis formation (Kemono & Piotrowska, 2020)	12
Figure 2.5	Many styrene (vinyl benzene) monomer units form a long styrene polymer chain by chemical bonding to manufacture polystyrene (Farrelly & Shaw, 2017)	13
Figure 2.6	Classification of Fibres (Onuwe et al., 2018)	16
Figure 2.7	Examples of continuous reinforcements (Campbell, 2010)	17
Figure 2.8	Examples of discontinuous reinforcements (Campbell, 2010)	17
Figure 2.9	Classification of Natural Fibres (Mohanty et al., 2005)	18
Figure 2.10	Classification of Plant or Vegetable Fibres (Mohanty et al., 2005)	19
Figure 2.11	Palm oil fibres	20
Figure 2.12	Correlation between thermal conductivity and density (Ramli et al., 2002)	23
Figure 2.13	Core region and bast region from kenaf stem (Hassan et al., 2017)	25
Figure 2.14	Kenaf bast fibres	27
Figure 2.15	The chemical structure of epoxy resin (Kausar, 2017)	33
Figure 2.16	Schematic diagram of vacuum infusion method (Hashim et al., 2017)	38
Figure 2.17	Tensile strength against OPEFB fibre loading (wt.%) (Ahmad et al., 2010)	41
Figure 2.18	Young's modulus against OPEFB fibre loading (wt.%) (Ahmad et al., 2010)	41
Figure 2.19	Tensile strength of composites at various kenaf loadings (Öztürk, 2010)	42

Figure 2.20	Transverse thermal conductivity of the composite versus volume fraction of fibre (Behzad & Sain, 2007)	44
Figure 2.21	Tensile Strength of untreated and treated OPPF/Epoxy composites (Obasi et al., 2014)	46
Figure 2.22	Tensile Moduli of untreated and treated OPPF/Epoxy Composites (Obasi et al., 2014)	47
Figure 2.23	SEM image of composite of wheat gluten and palm fibre treated with 5 w/v% NaOH (Chaiwong et al., 2019).	48
Figure 2.24	Untreated fibre (Mahjoub et al., 2014)	49
Figure 2.25	Treated fibre with 5% NaOH solution (Mahjoub et al., 2014)	50
Figure 3.1	Palm oil fibre	52
Figure 3.2	Kenaf bast fibre	52
Figure 3.3	Flowchart for the overall experimental processes	55
Figure 3.4	(a) Schematic diagram and (b) experimental setup of vacuum infusion method	61
Figure 3.5	Tensile test experiment	63
Figure 3.6	Samples were soaked in the distilled water	64
Figure 3.7	Heat conduction equipment	66
Figure 4.1	SEM image of untreated palm oil fibre at 400x magnification	69
Figure 4.2	SEM image of alkaline treated palm oil fibre at 400x magnification	69
Figure 4.3	SEM image of untreated kenaf fibre at 400x magnification	70
Figure 4.4	SEM image of alkaline treated kenaf fibre at 400x magnification	71
Figure 4.5	Representative FTIR spectra of untreated and treated palm oil fibre	74
Figure 4.6	Representative FTIR spectra of untreated and treated palm oil fibre composite	74
Figure 4.7	Representative FTIR spectra of untreated and treated kenaf fibre	77
Figure 4.8	Representative FTIR spectra of untreated and treated kenaf fibre composite	78
Figure 4.9	Representative FTIR spectra of epoxy resin	79

Figure 4.10	Tensile strength of untreated and treated palm oil fibre composites at different fibre loadings	82
Figure 4.11	Tensile modulus of untreated and treated palm oil fibre composites at different fibre loadings	83
Figure 4.12	Stress-strain of untreated and treated palm oil fibre composites curve at (a) 20 vol.% fibre loadings, (b) 30 vol.% fibre loadings, and (c) 40 vol.% fibre loadings	85
Figure 4.13	Tensile strength of untreated and treated kenaf fibre composites at different fibre loadings	88
Figure 4.14	Tensile modulus of untreated and treated kenaf fibre composites at different fibre loadings	89
Figure 4.15	Stress-strain of untreated and treated kenaf fibre composites curve at (a) 20 vol.% fibre loadings, (b) 30 vol.% fibre loadings, and (c) 40 vol.% fibre loadings	91
Figure 4.16	Tensile fracture of 20 vol.% palm oil fibre composites at 35x magnification, (a) 20UPOF and (b) 20TPOF	93
Figure 4.17	Tensile fracture of 30 vol.% palm oil fibre composites at 35x magnification, (a) 30UPOF and (b) 30TPOF	94
Figure 4.18	Tensile fracture of 40 vol.% palm oil fibre composites at 35x magnification, (a) 40UPOF and (b) 40TPOF	96
Figure 4.19	Tensile fracture of 20 vol.% kenaf fibre composites at 35x magnification, (a) 20UKF and (b) 20TKF	97
Figure 4.20	Tensile fracture of 30 vol.% kenaf fibre composites at 35x magnification, (a) 30UKF and (b) 30TKF	98
Figure 4.21	Tensile fracture of 40 vol.% kenaf fibre composites at 35x magnification, (a) 40UKF and (b) 40TKF	100
Figure 4.22	Water absorption of UPOF and TPOF composites curve at (a) 20 vol.% fibre loadings, (b) 30 vol.% fibre loadings, and (c) 40 vol.% fibre loadings	103
Figure 4.23	The presence of polar groups that form strong hydrogen bonds between water molecules and cellulose (Alodan et al., 2018)	107
Figure 4.24	Water absorption of UKF and TKF composites curve at (a) 20 vol.% fibre loadings, (b) 30 vol.% fibre loadings, and (c) 40 vol.% fibre loadings	109
Figure 4.25	DSC curve of untreated palm oil fibre composite	113

Figure 4.26	DSC curve of treated palm oil fibre composite	114
Figure 4.27	DSC curve of untreated kenaf fibre composite	116
Figure 4.28	DSC curve of treated kenaf fibre composite	116
Figure 4.29	Thermal conductivity of untreated and treated palm oil fibre composites at different fibre loadings	118
Figure 4.30	Thermal conductivity of untreated and treated kenaf fibre composites at different fibre loadings	120
Figure 4.31	Tensile strength of polystyrene foam and palm oil fibre composites with different fibre loadings	122
Figure 4.32	Tensile modulus of polystyrene foam and palm oil fibre composites with different fibre loadings	122
Figure 4.33	Water absorption of polystyrene foam and palm oil fibre composites with different fibre loadings	124
Figure 4.34	Thermal conductivity of polystyrene foam and palm oil fibre composites with different fibre loadings	126

LIST OF ABBREVIATIONS

ASTM	American Society for Testing and Materials
DSC	Differential Scanning Calorimetry
FTIR	Fourier Transform Infra-Red
EFB	Empty Fruit Bunch
EPA	Environmental Protection Agency
EPS	Expanded Polystyrene
H ₂ O	Chemical formula of water
HIPS	High Impact Polystyrene
MPOB	Malaysian Palm Oil Board
Na	Sodium
N ₂	Chemical formula of nitrogen
NaOH	Sodium Hydroxide
OH	Hydroxide
OPEFB	Oil Palm Empty Fruit Bunch
OPPF	Oil Palm Press Fibre
Pd	Palladium
PLA	Polylactic Acid
PU	Polyurethane
PS	Polystyrene
RM	Ringgit Malaysia
RTM	Resin Transfer Moulding
TPOF	Treated Palm Oil Fibre
TKF	Treated Kenaf Fibre
T _c	Crystallisation Temperature

T_g	Glass Transition Temperature
T_m	Melting Temperature
UPOF	Untreated Palm Oil Fibre
UKF	Untreated Kenaf Fibre
UTM	Universal Testing Machine
SEM	Scanning Electron Microscope



LIST OF SYMBOLS

%	Percentage
ρ	Density
cm	Centimetre
λ	Thermal conductivity
cm ³	Centimetre cube
°C	Degree Celsius
C	Carbon
G	Gram
GPa	Giga Pascal
g/cm ³	Gram per centimetre cube
h	Hour
H	Hydrogen
kg/m ³	Kilogram per metre cube
kPa	Kilo Pascal
kV	Kilo Voltage
kN	Kilo Newton
K	Thermal conductivity
m	Meter
ml	Millilitre
mm	Millimetre
ml/min	Millimetre per minute
MPa	Mega Pascal
O	Oxygen
Psi	Pounds per square inch

vol.%	Volume percent
W	Watt
w/v%	Weight by volume percent
wt.%	Weight percent



CHAPTER ONE

INTRODUCTION

1.1 BACKGROUND

In recent years, natural fibre as reinforcement which include plant fibres and wood fibres has increased dramatically and has become more essential. This is due to natural fibre is a renewable resource and it has been discovered and used because non-renewable resources are becoming scarce (Gholampour & Ozbakkaloglu, 2020). Animals, vegetables as well as minerals are obtained and they are produced into a class of hair-like materials and they are called natural fibres. Some of them spun into filaments, thread, or rope. Besides that, they can be utilized as reinforcements and will be embedded in matrix to form fibrous composites (Bhardwaj et al., 2015). A composite material is defined as materials that are made up off two or more materials, each of them has various type of physical as well as chemical properties. However, when it is combined, it will form a new material with some different characteristics from the individual material (Nagavally, 2017).

Currently, producing automotive components from natural fibre composites are already exists in the manufacturing industry (Ramli et al., 2018). Germany was one of the pioneer in utilizing natural fibre composites for interior and exterior of car applications. For instance, the inner door panel was first introduced in 1999 of the S-Class MercedesBenz (Koronis et al., 2013). Furthermore, epoxy matrix with the addition of jute was used for the door panels in its E-class vehicles of the Mercedes Benz back in 1996 (Foaisal et al., 2009). In 2008, another development was announced at the EcoInnovAsia 2008 event held in Bangkok, Thailand which was related to Mazda

5. The manufacturer used polylactic acid (PLA) for the interior consoles with PLA and kenaf fibre in the seat covers (Broeren et al., 2017). Besides that, door panels of the car Ford Mondeo in UK, are made of kenaf fibre and polypropylene resins. Hence, by utilizing kenaf fibre as a door panel could reduce the mass of the door from 5% to 10% (Jović & Milićević, 2017). However, there were limited research on utilizing natural fibre composites in exterior automotive components especially in the refrigerated vehicle wall.

The temperature controlled vehicles are called refrigerated vehicles that are used to transport raw food and food products for instance, dairy products, meats and ice-creams from the farm of producer to the market customers (Baartmans, 2015; Isaksson et al., 2016;). The purpose of refrigerated vehicles is to maintain the chilling temperature that avoids shelf life spoilage while cooling chamber provides cooling. Refrigerated vehicle's body is made up of insulating material sandwiched in two metal sheets of aluminium or steel (Beukers et al., 1999; Heisler, 2002; Tassou et al., 2009). Insulation material such as polyurethane foam and polystyrene foam are mostly used as insulation material because it helps to preserve the temperature in the panel outer surface (Al-Homoud, 2005; Baetens et al., 2010; Yang et al., 2015; Ravago, 2020). However, polyurethane and polystyrene are non-renewable and non-biodegradable resources. Polyurethanes (PU) are derived from the petrochemical industry and are generally synthesized by the polyols (Lligadas et al., 2010; Kong et al., 2012; Cinelli et al., 2013) while polystyrene (PS) is a durable thermoplastic that is generally believed to be non-biodegradable (Kaplan et al., 1979; Ho et al., 2018). It is always a critical job for researchers to overcome the environmental issues by using non-biodegradable materials (Chang and Lu, 2012; Fan et al., 2012; Spontón et al., 2013). Thus, in this

research, natural fibres such as kenaf fibres and palm oil fibres were used as one of the potential insulation materials due to their biodegradable and renewable resources.

There are various of factors that needed to be taken into account when designing insulation core material of refrigerated truck bodies. The vehicles must be insulated effectively by having low thermal conductivity as they are designed to transport easily-perishable food (Uwa. et al., 2019; Ravago, 2020). Besides that, the core material must be capable to withstand high mechanical force when loaded with heavy cargo loads, during loading and unloading (Ravago, 2020). In addition, refrigerated vehicle walls required low moisture pick up in order to prevent any damages to the exterior or interior that may occur during on or off-loading as well as daily services. The moisture resistance of the core insulation material can have a significant impact on long term insulation performance of truck panels (Ravago, 2020). As a result, the goal of this study is to use kenaf fibre composites and palm oil fibre composites as a replacement for polystyrene foam used for core insulation materials in refrigerated vehicles, with the potential for low thermal conductivity, high tensile properties, and low water absorption behaviour.

1.2 PROBLEM STATEMENT

More sustainable developments in automotive industry was in demands due to fuel-efficient and low polluting vehicles revolutions. A lot of studies indicated that the car industry had utilized natural fibres as the developments in the automotive industry. For instance, flax, kenaf, hemp and jute and these were basically used and to be applied within the passenger cars (Dammer et al., 2013). On top of that, natural fibre composites have been used in interior automotive components for instance interior door panel, headliners, seatbacks and package trays (Tholibun et al., 2019). However, there were

limited research on utilizing natural fibre composites in exterior automotive components especially in the refrigerated vehicle wall.

Generally, refrigerated vehicle wall which takes the shape of a box and is made up of insulating material sandwiched in two metal sheets of aluminium or steel (Heisler, 2002; Tassou et al., 2009; Ravago, 2020). Insulation material that is being used the most is polystyrene foam or is also known as a core material (Yang et al., 2015; Ravago, 2020). Polystyrene (PS) is a petroleum-based plastic made from styrene (vinyl benzene) monomer and it is generally believed to be non-biodegradable (Ho et al., 2018). Otake

Therefore, in this work, kenaf fibre and oil palm empty fruit bunch fibre (EFB) were used due to their low cost, biodegradable and found abundance in Malaysia (Yousif et al., 2012; Faruk et al., 2012). Moreover, the utilization of EFB which is a by-product of palm oil refinery can ease the agricultural waste disposal issue and kenaf fibre has been well known for its long history as reinforcement in polymer composites (Akil et al., 2011). However, the susceptibility of natural fibre towards moisture absorption is one of the drawbacks that restricts the use of natural fibre as reinforcement in composites (Alamri et al., 2012). This is due to their hydrophilic characteristic as they tend to absorb moisture from the environment and swell. Hence, the presence of voids at the fibre-matrix interface which consequently lead to reduction of mechanical and physical properties (Ngo et al., 2014). Alkaline treatment by using sodium hydroxide was used in this work to treat the fibres in order to improve the interfacial adhesion between the fibre and matrix (Majid et al., 2016).

Besides that, the mechanical and physical properties of producing insulating core material from the refrigerated truck bodies were good thermal insulation, low water absorption and high mechanical strength properties (Ravago, 2020). Thus, in this study, the mechanical and physical properties of natural fibre composites were investigated in